



Comparative Study on the Photovoltaic Properties of Dye-Sensitized Solar Cells (DSCs) Based on Different Counter Electrode Configurations

T. O. Ahmed^{1*}, N. Alu² and A. Y. Abdul Rahman¹

¹Department of Physics, Faculty of Science, Federal University Lokoja (FUL), Lokoja, Nigeria.
²Physics Advanced Research Centre, Sheda Science and Technology Complex, Abuja, Nigeria.

Authors' contributions

This work was carried out in collaboration among all authors. Authors TOA and NA designed the study. Author TOA wrote the protocol and wrote the first draft while, authors NA and AYAR carried out the experimental work and analyses. Authors TOA and AYAR managed the literature searches. All authors read and approved the final manuscript.

Article Information

Editor(s):

(1) Dr. Madogni Vianou Irenée, Département de Physique, Laboratoire de Physique du Rayonnement LPR, Cotonou, Université d'Abomey-Calavi (UAC), Bénin.

Reviewers:

- (1) Bankole Adebajji, Ekiti State University, Nigeria.
(2) Dr. Hafiz Muhammad Ali, University of Engineering and Technology Taxila, Pakistan.
(3) Boussaibo André, University of Ngaoundéré, Cameroon.
Complete Peer review History: <http://www.sdiarticle3.com/review-history/47570>

Original Research Article

Received 22 December 2018
Accepted 28 February 2019
Published 27 April 2019

ABSTRACT

Previously, we reported an investigation on Delonix regia dye extract as a natural sensitizer for TiO_2 /DSC assembled with platinum counter electrode and low power conversion efficiency was recorded. This necessitated the current investigation on *Delonix regia* dye extract as a natural sensitizer for TiO_2 /DSCs assembled with different counter electrodes. Platinum counter electrode was used for one of the DSCs while polyaniline (PANI) was used to replace platinum in the other DSC. The vitriol treated PANI thin film consisted of aniline mixed with potassium dichromate directly reacted on circular graphite foam. The conductivity and Hall coefficient were measured to be $4.894 \times 10^{-1} \Omega^{-1} cm^{-1}$ and $2.061 \times 10^1 cm^3 C^{-1}$ respectively using ECOPIA Hall Effect Measurement System (HMS-3000 Version 3.52). Sequel to this, the DSCs were assembled and characterized using a standard overhead Veeco viewpoint solar simulator equipped with AM 1.5 filter to give a

*Corresponding author: Email: tajahmol@yahoo.co.uk, tajudeen.ahmed@fulokoja.edu.ng;

solar radiation of 1000 W/m^2 and coupled to a Keithley source meter (model 4200SCS) which was connected to the computer via GPIB interface for data acquisition. The overall solar power conversion efficiencies of 0.02% and 0.04% were obtained for *TiO₂-DSC//Delonix regia dye//platinum electrode* and *TiO₂-DSC//Delonix regia dye//PANI electrode* respectively. *Delonix regia dye extract* proved to be rather a poor sensitizer as can be seen by the low spectral absorption at lower energies with short circuit current density of 0.10 mAcm^{-2} and 0.11 mAcm^{-2} respectively. Nevertheless, a 10% decrease in the electron recombination via redox electrolyte and collection at the photoelectrode was observed for *TiO₂-DSC//Delonix regia dye//PANI electrode* and a 20% increase in the open circuit voltage (V_{oc}) was also observed. Finally, about 37% increase in the fill factor was observed for the *TiO₂-DSC//Delonix regia dye//PANI electrode* over *TiO₂-DSC//Delonix regia dye//platinum electrode*. This necessitated approximately 50% increase in the power conversion efficiency for the *TiO₂-DSC//Delonix regia dye//PANI electrode* over *TiO₂-DSC//Delonix regia dye//platinum electrode*.

Keywords: *Delonix regia dye extract; PANI counter electrode; TiO₂-DSC; short circuit current density; open circuit voltage; fill factor; power conversion efficiency.*

1. INTRODUCTION

Dye-sensitized Solar Cells (DSCs) are fast becoming promising alternatives to the conventional silicon based solar cells because of cheap fabrication cost coupled with easy fabrication steps that could lead to a myriad of shapes using flexible substrates to meet the need of various applications [1,2,3]. The salient features of a DSC include photoelectrode, photosensitizer, electrolyte (redox couple) and counter electrode [4,5]. However, the highest efficiency recorded to date is still well below that for the silicon based solar cells [6,7,8]. The major factor responsible for low energy conversion efficiency is the competition between generation and recombination of photo-excited carriers in DSCs [1]. As such, most of the efforts made so far are targeted toward the synthesis of new nanostructured working and counter electrodes to ameliorate this setback [9,10,11,12,13]. Sequel to this, surface modification of TiO_2 was studied by depositing SrTiO_3 on its surface to form a core-shell structure in order to shift its conduction band upward closer to the excited state of the coated dye causing enhancement in the open-circuit voltage [11]. As for the counter electrode, the research on the 3-dimensional nanostructure is currently ongoing but the increased surface area offers more locations for I_3^- reduction and also shortens the redox couple diffusion length. As a follow-up to this, a vertically aligned carbon nanotube counter electrode was fabricated for use in DSC and this led to an increased short-circuit current compared to that obtained using the conventional platinum counter electrode [12]. With platinum being a costly noble metal, reasonable efforts have been made to find cheaper alternatives [14]. Such efforts include the

use of porous polyaniline nanotube, graphene/polyaniline nanocomposite and microporous polyaniline [15,16,17,18]. These concerted efforts are tied to the fact that polyaniline showed lower charge transfer resistance and higher electrocatalytic activity for reduction of I_3^- into I^- than platinum [15,18]. Herein we report a carefully structured polyaniline (PANI) thin film as counter electrode for use in DSC so as to improve its energy conversion efficiency. The film consisted of aniline mixed with potassium dichromate and reacted on circular graphite foam directly to preserve the stoichiometry and prevent over oxidation of the aniline which would have reduced the conductivity. The vitriol treated PANI is a p-type semiconducting polymer with low mobility and conductivity values. The sign and value of the Hall coefficient also validated the nature of the carriers with $3.029 \times 10^{17} \text{ cm}^{-3}$ as the measured bulk concentration and thus can function as efficient counter electrode. In our previous study, we developed and characterized a DSC based on TiO_2 nanoparticles coated with delonix regia and the overall solar power conversion efficiency of 0.02% and a maximum current density of 0.10 mAcm^{-2} were obtained. Typically, low peak absorption coefficient, small spectra width and very low power conversion efficiency of this DSC boosted additional studies oriented; on one hand, to the use of modified photoelectrode and on the other hand, we hope to improve the power conversion efficiency with use of a semiconducting polymeric counter electrode. Sequel to this, two (2) DSCs; one with platinum counter electrode and the other with PANI counter electrode, were assembled and characterized using a standard overhead Veeco viewpoint solar simulator equipped with AM 1.5

filter to give a solar radiation of 1000 W/m^2 and coupled to a Keithley source meter (model 4200SCS) which was connected to the computer via GPIB interface for data acquisition.

2. MATERIALS AND METHODS

Titanium isopropoxide, Titanium nanoxide, acetylacetonate, ethanol, isopropanol, fluorine doped tin-oxide (FTO) conducting glass [11.40 ohm/m^2 , $(1.00 \times 1.00) \text{ cm}^2$], electrolyte (iodolyte-AN-50), sealing gasket (surlyn-SX1170-25PF), and screen-printable platinum catalyst, (Pt-catalyst T/SP) all were obtained from SOLARONIX. Dye extract has been obtained from the natural product (*Delonix regia*). A mixture of 0.3M of titanium isopropoxide, 1.2M acetylacetonate and isopropanol was spin coated three (3) times with different concentrations sequentially as blocking layer on the pre-cleaned fluorine doped tin-oxide (FTO) conducting glasses and sintered at 150°C for four minutes each time the deposition has been made. Subsequently, a paste of titanium nanoxide in propanol in the ratio 1:3 has been screen printed on the three (3) fluorine doped tin-oxide (FTO) conducting glasses and allowed to dry at 125°C in open air for 6 minutes. The FTO/TiO₂ glass electrodes have been sintered in a furnace at 450°C for 40 minutes and allowed to cool to room temperature to melt together the TiO₂ nanoparticles and to ensure good mechanical cohesion on the glass surface. Fresh leaves of *Delonix regia* have been crushed into tiny bits and boiled in 75ml of deionized water for 15 minutes. The residue has been removed by adopting simple physical filtering technique using muslin cloth and the resulting extract has been centrifuged to further remove any solid residue. The dye extract has been used directly as prepared for the construction of the DSCs at room temperature. A scattering layer of TiO₂ has been also deposited on the TiO₂ electrodes before the electrodes have been immersed (face-up) in the natural dye extract for 18h at room temperature for complete sensitizer uptake. This turned the TiO₂ film from pale white to sensitizer colour. The excess dye has been washed away with anhydrous ethanol and dried in moisture free air. The thickness of TiO₂ electrodes and the deposited scattering layers was determined using Dekker Profilometer. Surface morphology of the screen-printed TiO₂ nanoparticles has been observed using EVOI MA10 (ZEISS) multipurpose scanning electron microscope

operating at 20kV employing secondary electron signals while the corresponding Energy Dispersive Spectra (EDS) have been obtained using characteristic x-rays emitted by TiO₂ nanoparticles. The X-ray diffraction (XRD) pattern of the screen-printed TiO₂ nanoparticles at room temperature has been recorded using X-ray Diffractometer; Panalytical Xpert-Pro, PW3050/60, operating at 30mA and 40kV, with monochromatic Cu-K α radiation, of wavelength $\lambda = 1.54060 \text{ \AA}$. A scanned range $3-80.00553^\circ 2\theta$, with a step width of 0.001° has been used. The pattern has been analyzed and the peaks have been identified using ICDD data file (01-075-8897). The UV-Visible (UV-Vis) absorption measurements of the dye extract and the dye extract on the screen printed TiO₂ electrodes have been carried out with Avante UV-VIS spectrophotometer (model-LD80K). From these measurements, plots for the absorbance, Light Harvesting Efficiency (LHE) and molar extinction coefficient versus the wavelengths of interest have been obtained using the relevant expressions from [20]. Few drops each of aniline and K₂Cr₂O₇ have been coated on graphite foam by gently turning the graphite foam by hand to fabricate alternative counter electrode. The mixture has been grown directly on graphite foam to preserve the stoichiometry. After the process, a greenish thin film of polyaniline (PANI) has been formed atop the graphite foam signifying that there was no over oxidation of the aniline which would have reduced the conductivity. After drying, the surface of the counter electrode has been thereafter rinsed using vitriol (H₂SO₄). Subsequently, the electrical characteristics of the semiconducting PANI deposited on soda lime glass following the above process have been determined using ECOPIA HALL EFFECT MEASUREMENT SYSTEM (HMS-3000 VERSION 3.52). A DSC of 0.52 cm^2 active area has been assembled by sandwiching a surlyn polymer foil of $25 \mu\text{m}$ thickness as spacer between the photoelectrode and the platinum counter electrode and then hot-pressed at 80°C for 15s. A few drops of electrolyte have been introduced into the cell assembly via a pre-drilled hole on the counter-electrode and sealed using amosil sealant. In order to have good electrical contacts, a strip of wire has been attached to both sides of the FTO electrodes. Similarly, in assembling the modified DSC, the same process as above has been adopted but instead of platinum counter electrode PANI coated on circular graphite foam has been clamped onto the photoelectrode to form a monolithic cell of 0.78 cm^2 active area. Finally, the DSCs have been

subjected to current-voltage characterization using a standard overhead Veeco viewpoint solar simulator equipped with *Air Mass 1.5* (AM 1.5) filter to give a solar radiation of 1000 W/m^2 and coupled to *Keithley* source meter (model 4200SCS) which has been connected to the computer via *GPiB* interface for data acquisition. Subsequently, the working electrode and counter electrode of the DSC have been connected in turn to the positive and negative terminals of the digital *Keithley* source meter respectively. The bias was from short circuit to open circuit and has been obtained automatically using LabVIEW software from National Instruments Inc, USA. From the data, *I-V* curves have been plotted in real time for the DSCs under illuminated condition. Following this, the photovoltaic parameters viz; the open circuit voltage (V_{oc}) and short circuit current (I_{sc}) were obtained from the *I-V* curves for the cells. The fill factor (*FF*) and the power conversion efficiency for the cells have been obtained using the following relations:

$$FF = \frac{P_m}{V_{oc} \cdot I_{sc}} \quad (1)$$

$$\eta = \frac{FF \cdot V_{oc} \cdot J_{sc}}{I_{in}} \quad (2)$$

3. RESULTS AND DISCUSSION

The image presented in Fig. 1 obtained using characteristic x-rays emitted by TiO_2 nanoparticles has been observed at a magnification of 83.04kX. The uniform contrast in the image revealed TiO_2 to be practically isomorphic with titanium and oxygen being the dominant elements with concentration of about 99.9% as depicted in the EDS spectra (Fig. 1b). The morphology of TiO_2 nanoparticles is such that the particles are closely parked and spherical in shape. The average diameter of the particles is in the range of 25-40nm reflecting that TiO_2 nanoparticles are transparent and suitable for DSC application. The thickness of TiO_2 on the FTO conducting glass determined using Dekker Profilometer has been found to be 5.2 μm for each photoelectrode and that of the deposited scattering layers has been found to be 1 μm . The XRD pattern revealed the compound name for the TiO_2 electrode to be anatase syn., and the structure type is tetragonal with 3.53217Å as the *d-spacing* for the most prominent peak, $2\theta=25.2139^\circ$ (ICDD data file: 01-075-8897).

Other prominent peaks occur at $2\theta= 37.7883^\circ$, 48.0463° , 53.9110° , 55.0481° , 62.7104° and 75.1376° with *d-spacing* $d= 2.38075 \text{ \AA}$, 1.89370 \AA , 1.70073 \AA , 1.66826 \AA , 1.48160 \AA and 1.26338 \AA .

In Fig. 2, the dye extract exhibits absorption maxima slightly above 400nm and the most prominent shoulder occur slightly above 500 nm. But upon sensitization on TiO_2 , there was a decrease in the absorption maxima and shoulder with a cut off slightly above 600 nm. It has been reported that chemisorptions of anthocyanins on TiO_2 was due to alcoholic bound protons which condense with the hydroxyl groups present at the surface of nanostructured TiO_2 [19]. Such attachment to the TiO_2 surface stabilizes the excited state, thus shifting the absorption maximum towards the lower energy of the spectrum. In our study, a shift in the absorption maximum towards higher energy of the spectrum has been observed for the dye extracts adsorbed on TiO_2 . This observation suggests that there was weak adsorption of the dye extract onto TiO_2 surface which could be attributed to the high *pH* value and the long bond length of the *OH* groups present in the dye extract. The shift may also be attributed to the changing of the anthocyanin molecule from the more stable flavilium state to the unstable quinoidal state upon chelation.

It is an established fact that the light absorption by a dye monolayer is small since the cross section for photon absorption of most photosensitizers is much smaller than the geometric area occupied on the semiconductor surface, but with thin film semiconductor the obtainable LHE is usually close to unity [21]. In this work, we have used TiO_2 thin film of thickness 5.2 μm and the LHE of the dye extracts and the dye mixture adsorbed onto TiO_2 surface is close to unity.

The light harvesting efficiency values (usually obtained in percentages) are plotted against wavelengths as shown in Fig 3. The absorption band of the dye extract on TiO_2 becomes a bit discrete after sensitization but quite broad for the dye extract. Whilst the molar extinction coefficients are very high for the dye extract on TiO_2 but it turned out that only small area is being covered by the solar irradiance spectrum. Most notably, the spectra bandwidth is within the range of 150 nm to 200 nm and this could be significantly enhanced if the *pH* is lowered using organic solvent.


The electrical characteristics for PANI determined using ECOPIA HMS-3000 (VER 3.52) are tabulated in Table 1.

Table 1. Electrical characteristics for PANI


<i>Bulk concentration</i>	$3.029 \times 10^{17} \text{ cm}^{-3}$
<i>Mobility</i>	$1.009 \times 10^1 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$
<i>Sheet resistance</i>	$6.050 \times 10^5 \Omega$
<i>Resistivity</i>	$2.043 \Omega \text{ cm}$
<i>Magneto resistance</i>	$9.451 \times 10^4 \Omega$
<i>Conductivity</i>	$4.894 \times 10^{-1} \Omega^{-1} \text{ cm}^{-1}$
<i>Hall coefficient</i>	$2.061 \times 10^1 \text{ cm}^3 \text{ C}^{-1}$

It is evident from Table 1 that the polymeric counter electrode (PANI) is semiconducting and it is a p-type semiconducting polymer with low


mobility and conductivity values. The sign and the value of the Hall coefficient also validate the nature of the carrier. The bulk carrier concentration is $3.029 \times 10^{17} \text{ cm}^{-3}$. Current density and power versus voltage characteristics of the DSCs are plotted and shown in Fig. 4. The photovoltaic parameters are determined and tabulated in Table 2. The current density for the DSC with platinum counter electrode is 0.10 mA cm^{-2} while that for the DSC with PANI counter electrode is 0.11 mA cm^{-2} . This corresponds to 10% decrease in the electron recombination via redox electrolyte and collection at the photoelectrode. In the same light, a 20% increase in the open circuit voltage (V_{oc}) has been observed for the DSC with PANI counter electrode. Since the V_{oc} of an electrochemical cell

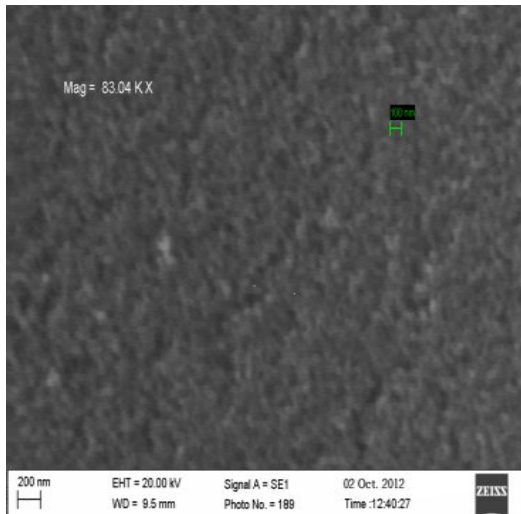

(a)

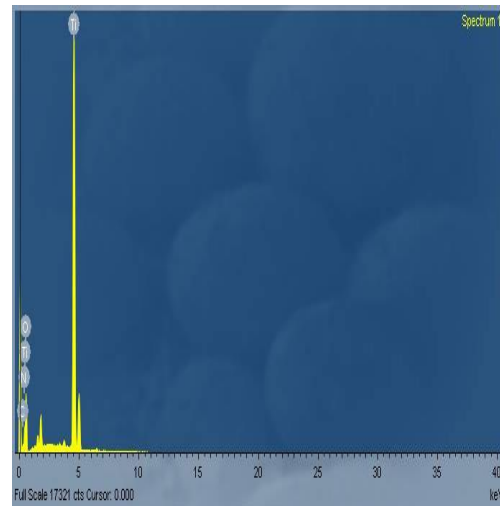

(b)

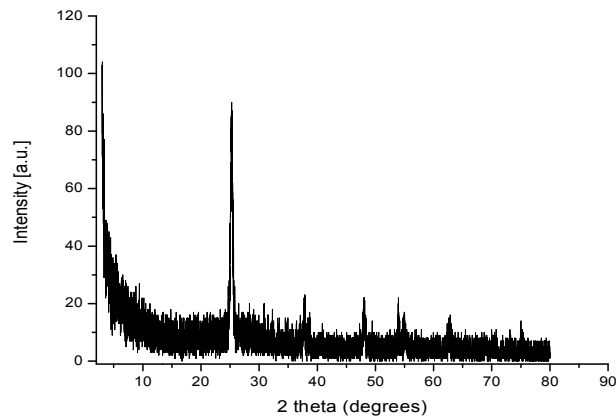

(c)

Fig. 1. TiO₂ structural characteristics. (a) Surface morphology, (b) EDS spectra and (c) XRD pattern for the screen printed TiO₂

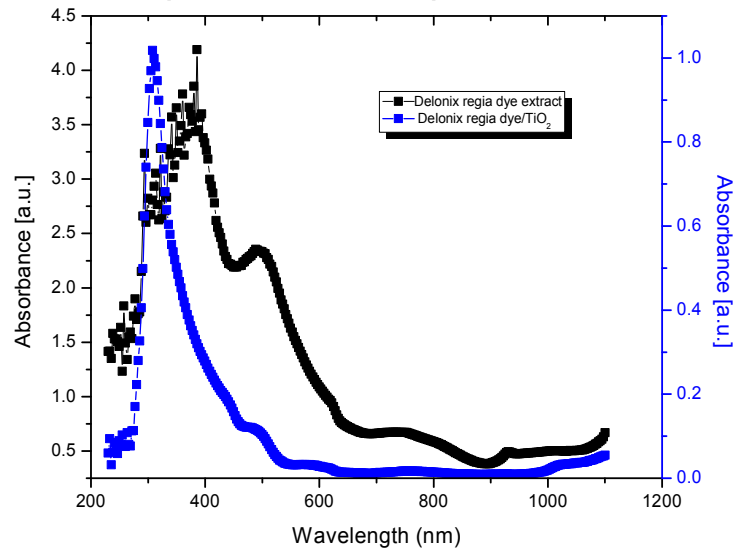


Fig. 2. Absorption versus wavelength (nm) for Delonix regia dye extract and Delonix regia/TiO₂

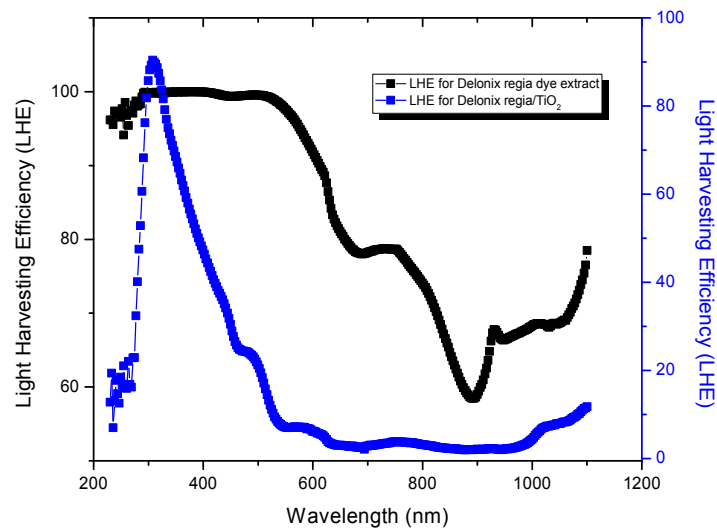


Fig. 3. Light Harvesting Efficiency (LHE) versus wavelength (nm) for Delonix regia extract and Delonix regia/TiO₂

is determined by the difference between the Fermi level of the semiconductor and the redox potential ($E_{f,redox}$) of the redox electrolyte then, the high V_{oc} observed for the monolithic DSC suggests that this difference in the Fermi levels is large. Generally the fill factor is influenced by the series resistance (R_s) arising from the internal resistance and resistive contacts of the cell and shunt resistance (R_{sh}) arising from the leakage of current. As such, about 37% increase in the fill factor has been observed for the DSC with PANI

counter electrode over the DSC with platinum electrode. Approximately, 50% increase in the power conversion efficiency was obtained for the DSC with PANI counter electrode over the DSC with platinum electrode. Thus, it is evident from Table 2 that high values of J_{sc} , and V_{oc} are responsible for the higher efficiency obtained for the DSC with PANI counter electrode over the DSC with platinum electrode. In our previous studies, we developed and characterized DSC based on TiO₂//Hibiscus sabdariffa//platinum

electrode and the overall solar power conversion efficiency of 0.033% and a maximum current density of 0.17mAcm^{-2} have been obtained [5]. This boosted additional studies oriented to the

Table 2. Photovoltaic parameters for DSCs sensitized with *Delonix regia* dye

DSC	$J_{sc}(\text{mAcm}^{-2})$	$V_{oc}(\text{V})$	FF	$\eta(\%)$
Movable TiO_2 -DSC with Platinum electrode	0.10	0.45	0.38	0.02
Monolithic TiO_2 -DSC with PANI electrode	0.11	0.56	0.60	0.04

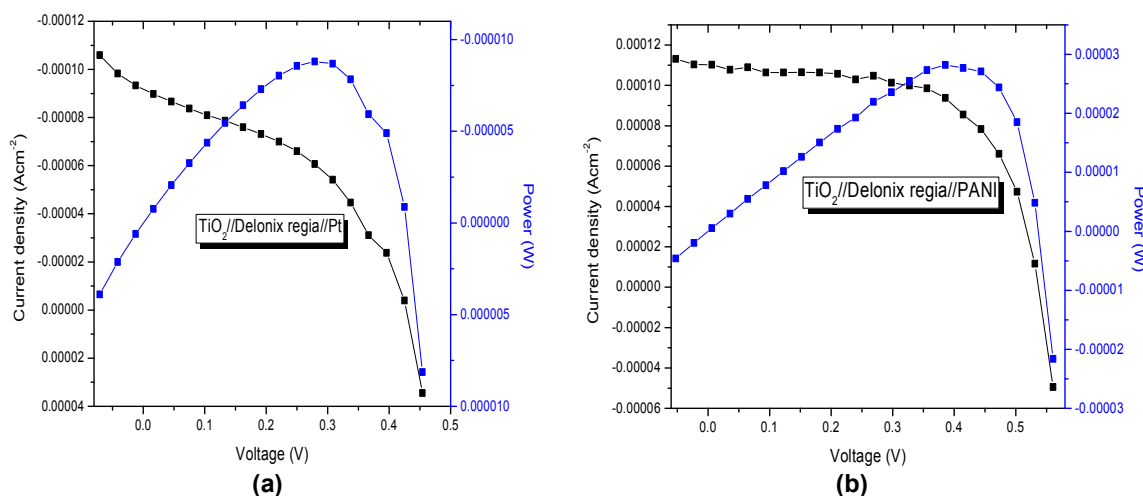


Fig. 4. Current density (J_{sc}) and Power (W) versus Voltage (V) for (a) TiO_2 -DSC//*Delonix regia* dye//Platinum electrode and (b) TiO_2 -DSC//*Delonix regia* dye//PANI electrode

use of anthocyanin dyes with alternative and modified components that would lead to an enhancement in the light harvesting efficiency and hence the photocurrent density which is owed to the high peak absorption coefficient and large spectra bandwidth. In this work, it was discovered that TiO_2 band gap has been reduced upon sensitization with the dye extract. The optical band gap obtained at the point where the absorption spectra showed a strong cut off, when the absorbance value is minimum is 2.40eV . The bands shift could be attributed to molecular transitions that take place when the dye molecules chelate with TiO_2 . Typically, anthocyanin dyes exhibit $\pi - \pi^*$ orbital transition which is attributed to the wavelength range between 500 nm to slightly above 650 nm .

In this work, the cut off wavelength for the spectra is slightly above 600 nm . Finally, it is well known that proton adsorption causes a positive shift of the Fermi level of the TiO_2 , thus limiting the maximum photovoltage that could be delivered by the cells [19]. Nevertheless, the TiO_2 -DSC//*Delonix regia* dye//PANI electrode proved to be a better cell compared to TiO_2 -DSC//*Delonix regia* dye//Platinum electrode that exhibited lower power conversion efficiency.

However, no deviation from this trend has been observed when the duration of continuous stimulated sunlight illumination has been increased for several hours.

4. CONCLUSION

In this work we reported an investigation on *Delonix regia* dye extract as natural sensitizer for TiO_2 -DSC//*Delonix regia* dye//platinum electrode and TiO_2 -DSC//*Delonix regia* dye//PANI electrode and the overall solar power conversion efficiencies of 0.02% and 0.04% have been obtained respectively under AM 1.5 irradiation. *Delonix regia* dye extracts proved to be rather a poor sensitizer as can be seen by the low spectral absorption at lower energies with current density of 0.10mAcm^{-2} and 0.11mAcm^{-2} respectively. Nevertheless, a 10% decrease in the electron recombination via redox electrolyte and collection at the photo-electrode has been observed for TiO_2 -DSC//*Delonix regia* dye//PANI electrode and a 20% increase in the open circuit voltage (V_{oc}) has been also observed. Furthermore, the high V_{oc} observed for the monolithic TiO_2 -DSC//*Delonix regia* dye//PANI electrode suggests that the difference between the Fermi level of the photoelectrode and the

redox potential ($E_{f,redox}$) of the redox electrolyte is large. Finally, about 37% increase in the fill factor has been observed for the TiO_2 -DSC//Delonix regia dye//PANI electrode over TiO_2 -DSC//Delonix regia dye//platinum electrode. This necessitated approximately 50% increase in the power conversion efficiency for the TiO_2 -DSC//Delonix regia dye//PANI electrode over TiO_2 -DSC//Delonix regia dye//platinum electrode. Although the efficiencies obtained with this natural dye extract are still below the current requirement for large scale practical application, the results are encouraging and may boost additional studies oriented to the optimization of solar cell components compatible with the dye. In view of this, we are currently exploring the possibility of increasing the power-conversion efficiency of the DSCs based on TiO_2 using modified TiO_2 and counter electrodes and Delonix regia.

ACKNOWLEDGEMENTS

We thank Physics Advanced Laboratory, Sheda Science and Technology Complex, FCT, Abuja, Nigeria for technical assistance during the experimental characterization.

COMPETING INTERESTS

Authors have declared that no competing interests exist.

REFERENCES

1. Brabec CJ, Sariciftci S, Hummelen JC. Plastic solar cells. *Advanced Functional Materials*. 2001; 1:15.
2. Ameri T, Dennler G, Lungenschmied C, Brabec J. Organic Tandem cells, *Energy Environ. Sci.* 2009;2:347.
3. Li J, Grimsdale AC. Carbazole-based polymer for organic photovoltaic cells. *Chem. Soc. Rev.* 2010;39:2399.
4. Hagfeldt A, Boschoo G, Sun L, Kloo L, Pettersson H. Dye-sensitized solar cells. *Chem. Rev.* 2010;110(10):6595-6663.
5. Ahmed TO, Akusu PO, ALU N, Abdullahi MB. Dye-sensitized solar cells based on TiO_2 nanoparticles and *Hibiscus sabdariffa*. *British Journal of Applied Science and Technology (BJAST)*. 2013;3(4):840-846.
6. Gratzel M. Dye-sensitized solar cells. *Journal of Photochemistry and Photobiology C: Photochemistry Reviews*. 2003;4:145.
7. Daeneke T, Kwon T, Holmes AB, Duffy NW, Bacch U, Spiccia L. High-efficiency dye-sensitized solar cells with ferrocene-based electrolytes. *Nature Chem.* 2011;3(3):211-215.
8. Yella A, Lee H, Tsao HN, Yi C, Chandiran AK, Nazeerudin MK, Diao EW, Yeh C, Zakeeruddin SM, Gratzel M. Porphyrin-sensitized solar cells with cobalt (II/III)-based redox electrolyte exceed 12% Efficiency. *Science*. 2011;334:629.
9. O'Regan B, Gratzel M. A low cost, high efficiency solar cell based on dye sensitized colloidal TiO_2 films. *Nature*. 1991;353:737.
10. Bach U, Lupo D, Comte P, Moser JE, Wiessortel F, Salbeck J, Spreitzer H, Gratzel M. Solid-state dye-sensitized mesoporous TiO_2 solar cells with high photon-to-electron conversion efficiencies. *Nature*. 1998;395:583.
11. Diamant Y, Chen SG, Melamed O, Zaban A. Core-shell nanoporous electrode for dye sensitized solar cells: The effect of the $SrTiO_3$ shell on the electronic properties of the TiO_2 core. *J. Phys. Chem. B*. 2003;107:1977-1981.
12. Sayer RA, Hodson SL, Fisher TS. Improved efficiency of dye-sensitized solar cells using a vertically aligned carbon nanotube counter electrode. *J. Solar Energy Engin.* 2010;132(2): 021007-021011.
13. Rahman MM, Kojima R, Fihry MEF, Tadaki D, Ma T, Kimura Y, Niwano M. Effect of porous counter electrode with highly conductive layer on dye-sensitized solar cells. *Japanese Journal of Applied Physics*. 2011;50(8).
14. Thomas S, Deepak TG, Anjusree GS, Arun TA, Nair SV, Nair AS. A review on counter electrode materials in dye-sensitized solar cells. *Journal of Material Chemistry A*. 2014;13.
15. Li Q, Wu J, Tang Q, Lan Z, Li P, Lin J, Fan L. Application of microporous polyaniline counter electrode for dye-sensitized solar cells. *Electrochemistry Communications*. 2008;10(9):1299-1302.
16. Wang G, Zhuo S, Xing W. Graphene/polyaniline nanocomposite as counter electrode of dye-sensitized solar cells. *Materials Letters*. 2012;69:27-29.
17. Dwivedi G, Guncha MG, Bhaskarwar AN. Natural dye-sensitized solar cells with polyaniline counter electrode. *International*

- Proceedings of Chemical, Biological and Environmental Engineering. 2015;90.
18. Park KH, Kim SJ, Gomes R, Bhaumik A. High performance dye-sensitized solar cell by using porous polyaniline nanotubes as counter electrode. Chemical Engineering Journal. 2015;260: 393-398.
 19. Hao S, Wu J, Huang Y, Lin J. Natural dyes as photosensitizers for dye-sensitized solar cell. Solar Energy. 2006;80:209.
 20. Ooyama Y, Harima Y. Photophysical and electrochemical properties, and molecular structures of organic dyes for dye-sensitized solar cells. Chem. Phys. Chem. 2012;13(18):4032–80.
 21. Gratzel M. Solar energy conversion by dye-sensitized photovoltaic cells. Inorganic Chemistry. 2005;44:6841.

© 2019 Ahmed et al; This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:
The peer review history for this paper can be accessed here:
<http://www.sdiarticle3.com/review-history/47570>