



# **An Overview of the Green Road to the Synthesis of Nanoparticles**

**A. A. Ramanathan<sup>1\*</sup> and M. W. Aqra<sup>2</sup>**

<sup>1</sup>*Department of Physics, The University of Jordan, Amman, Jordan.*

<sup>2</sup>*National Center for Research and Development, (NCRD), Amman, Jordan.*

### **Authors' contributions**

*This work was carried out in collaboration between both authors. Author AAR conceived the project, researched the literature, designed, wrote and revised the paper. Author MWA did the background literature study, organized the material, wrote the manuscript and corrected the proof. Both authors read and approved the final manuscript.*

### **Article Information**

DOI: 10.9734/JMSRR/2019/46014

#### Editor(s):

(1) Dr. Azzuliani Binti Supangat, Senior Lecturer, Low Dimensional Materials Research Centre, Department of Physics, Faculty of Science, University Malaya, Malaysia.

#### Reviewers:

(1) Abdallah Mahmoud Ahmed Hassane, Assiut University, Egypt.  
(2) Shahnaz Majeed, Universiti Kuala Lumpur Royal College of Medicine Perak, Malaysia.  
Complete Peer review History: <http://www.sdiarticle3.com/review-history/46014>

**Review Article**

**Received 12 October 2018**  
**Accepted 28 December 2018**  
**Published 15 January 2019**

## **ABSTRACT**

The world today is witness to the exponential rise of nanotechnology in our daily lives with a vast number of applications in energy, medicine, food, water, cosmetics and drugs. The attractive properties of materials in the nanoscale have brought to light many new discoveries and innovative applications of nanoparticles (NPs). The progress and implementation of this new and exciting technology requires caution especially during nanoparticle production and synthesis. The fabrication of these all important NPs should be done in a clean, cheap, sustainable and safe manner with minimum risk to health and environment. This article reviews and reports eco-friendly, sustainable and energy efficient green methods of synthesizing NPs, with low environmental pollution and health hazards. Our aim is to highlight and summarize the use of green synthesis methods that use biological units, namely, plants and microorganisms (bacteria, yeast and fungi) for the production of inorganic NPs, with a focus on research works during the last five years. The added advantage of disease inhibition of NPs produced using the green approach, due to their excellent antibacterial, antifungal and antitumor properties, has also been discussed and illustrated with specific examples from literature.

\*Corresponding author: Email: [amallahmad@gmail.com](mailto:amallahmad@gmail.com);

*Keywords: Nanoparticles; environmental safety; green synthesis; plants; microorganisms; antibiotic.*

## 1. INTRODUCTION

All matter and life originates at the nanoscale with atoms and molecules and this provides us with a very useful set of tools and techniques called nanotechnology, which includes nanoparticles (NPs), nanofabrication, nanobiotechnology and other cognitive sciences. The unifying force is the manipulation of nanoscale matter for the diverse applications that we see today. Nanomaterials have dimensions of 1-100 nm and the main appeal is their large surface to volume ratio which gives them unique and enhanced properties. The size, shape and type of the NPs greatly influence its properties and the field of applications. Nanomaterials find applications in environment and toxic gas sensing [1-5], food and agriculture [6,7], drugs and medicine [8-12] and in energy [13-15].

While nanotechnology makes many things in life easier and provides benefits to society, the large scale production of nanomaterials and the use of self replicating nano-machinery can pose incalculable risks. It is important to understand the role of nanoparticles in the uptake of pollutants and nutrients and also the toxicity of nanoparticles in food and agriculture. Safer design and manufacturing practices have to be adopted to ensure minimum risk to environment and human health. The concerns of toxicity and energy efficiency have lead to substantial research on green and sustainable production of NPs. This is a rapidly growing research field and the last two decades have witnessed the use of biological resources such as plants, microorganisms and natural biomolecules for reduction and stabilization of a large number of NPs [16-20]. This mini review focuses on the recent literature mainly last five years, to highlight and summarize the green synthesis routes, which use biological units from plant, bacteria, fungi and yeast with sustainable and energy saving protocols for NPs fabrication. The review emphasizes through published data that NPs of a wide range of chemical composition, size and shape, with the minimum of environmental contamination are possible using green synthesis and varying experimental parameters. The important added benefit of disease inhibition through the excellent antibacterial, antimicrobial and antitumor properties of green NPs is also explored and illustrated using specific examples from literature. The review is organized under the sections: importance of green synthesis, methods

of green synthesis, disease inhibition using green NPs and conclusions.

## 2. GREEN SYNTHESIS AND WHY IT IS IMPORTANT

### 2.1 What is Green Synthesis?

Green synthesis is the production of NPs using natural resources like plant extracts, microorganisms and energy saving methods in a sustainable, non-toxic and economical way. Extracts from different plants can be used to produce NPs with special characteristics and functionality to suit a specific application [10,21,22]. The microorganisms can be bacteria, fungi, yeasts and the choice will be based on the type, size and functionality that are desired of the NPs [23-25].

### 2.2 Benefits of Green Synthesis

Why use green synthesis when conventional methods of production exist? The answer lies in the numerous benefits that come with the use of a green route for NPs synthesis. First of all, NPs produced in this manner are more stable and effective in comparison with those produced by physicochemical methods. Next, they are eco-friendly, sustainable, inexpensive and free of contaminants. In comparison physicochemical methods are costly and can be unhealthy (as a result of toxic chemicals used) with high chances of contamination. Purity of NPs is a major consideration for biological and medical applications and green NPs are mostly contaminant free. In addition, they are energy efficient and do not need high pressure, temperature, or toxic chemicals. Moreover, most NPs produced by the green method show excellent antifungal, antibacterial and anti-parasitic properties. Other advantages are the ease of large scale synthesis and the disposal of the non-toxic waste products.

## 3. METHODS OF GREEN SYNTHESIS

The production of nanoparticles (NP) using natural substances is an important and emerging area in nanotechnology. The conventional methods of synthesis of NPs using chemicals as precursors or reducing agents have potential risks of toxicity and in general are not environmentally friendly or quick processes. To overcome these disadvantages the use of

renewable resource natural biological systems to produce NPs is finding widespread acceptance. The different methods of green synthesis will be expanded based on the type of resource used and classified under: a) use of plants and plant extracts b) use of microorganisms and c) use of energy saving methods.

### 3.1 Use of Plants and Plant Extracts

Green synthesis using biological molecules from plant extracts has proved to be far superior to chemical means. Plants are readily available, diverse and safe making them very appealing as sustainable bio resources. The huge plant diversity provides a natural bank of resources that can be utilized to rapidly synthesize in a one step protocol different types of NPs having a range of antimicrobial activity and applications. The reaction rate of plant mediated NPs synthesis is rather fast (few minutes to hours) and occurs mainly at room temperature leading to easy scalability. The use of plant extracts to produce NPs of high quality, specific morphology and function is wide spread due to the simple steps involved in nanoparticle recovery. Fig. 1 shows a schematic diagram of the steps involved from [26]. The steps involved are extraction of plant by hand grinding/blender, filtration of the extract, addition of metal NP salt, stirring the resultant solution and finally recovery of NPs from precipitate.

Different parts of the plant like stem, fruit, fruit peels, bark, root and leaves can be used to produce the NPs. Taking silver (Ag) NPs as an example, the specific parts of the various plants used for synthesis is presented in Table 1 adapted from Ahmed et al. [10].

The advantage of using plant extracts over other biological methods is that there is no need for elaborate culturing or cell maintenance. Another attractive feature is its easy scalability in comparison with microorganisms [10,36]. The success of producing metal, metal oxide and chalcogenide NPs with excellent antimicrobial properties by this method for various applications has been reported in several research articles and reports [10,21,22,26-39].

### 3.2 Use of Microorganisms

Many microorganisms can be considered as nano factories that produce metal nanoparticles with different efficiency, size and shape. The use of

physical and chemical means for NP synthesis may result in contamination due to toxic solvents, precursors and generate harmful byproducts with generally low yields. In contrast, the use of microorganisms like fungus, yeast and bacteria for NPs synthesis is relatively nontoxic, safe, reliable, clean and environmentally friendly with high yields [17-20,40-42]. Due to the ease of control of yeast under laboratory conditions, availability of numerous enzymes and the rapid growth with the use of simple nutrients, the yeast strains are preferred over bacteria [20]. Fungi have the ability to digest extracellular food and excrete enzymes that hydrolyze complex molecules to simpler ones. Thus, they act as reducing agents of metal salts through secretion of enzymes and proteins to yield NPs. The mechanism may be extracellular that is outside the cell or between group of cells or intracellular meaning inside the cell or cytoplasm. This form of biosynthesis has great potential as large scale production of NPs from various strains of fungi is possible and they can even be grown *in vitro*. Table 2 lists some of the noble metal, metal oxide, chloride and sulphide NPs obtained from diverse fungi and yeast species [43-55]. The extraction of NPs synthesized through intercellular mechanism requires extra processing steps, so extracellular is favored in most microbial approaches, as seen in Table 2.

The extracellular biosynthesis of Ag NPs using filamentous fungi like '*Aspergillus fumigatus*' has been reported by Kuber et al. [23]. Well dispersed Ag NPs of 5-25 nm were formed within minutes of silver ion coming in contact with the cell filtrate showing that the extracellular reduction process is a very fast and feasible biosynthesis method for Ag NPs. These filamentous fungi are excellent candidates for extracellular process applications, since, they secrete a variety of enzymes and are easy to grow and handle.

'*Fusarium oxysporum*' is one of the most utilized filamentous fungal species for production of NPs. The work of Govender et al. [55] shows the successful reduction of octahedral  $H_2PtCl_2$  and  $PtCl_2$  by the hydrogenase enzyme released from *Fusarium oxysporum*. This is a two step process; first at a pH of 9 and 65°C, the large  $H_2PtCl_2$  molecule undergoes a two electron reduction to a smaller  $PtCl_2$  molecule that can fit the enzyme surface, then at an optimal hydrogenase enzyme activity of pH of 7.5 and 35°C a second two electron reduction of  $PtCl_2$  occurs to give Pt NPs.

Another typical example using '*Fusarium oxysporum*' is the size controlled synthesis of silver NPs to obtain well-dispersed nanoparticles with size between 5 and 13 nm by Hussein et al. [9]. The NP type, size and morphology are controlled by the environmental and nutritional parameters via substrate concentration, temperature, pH and weight of biomass.

The biosynthesized NPs showed excellent antibacterial and antitumor activities which will be discussed in more detail in section IV.

### 3.3 Use of Energy Saving Methods

The synthesis of molybdenum disulfide nanostructures (MSNs) for host of applications by the 'green' microwave-assisted (MW) solvothermal synthesis method [56] is a clear example of energy saving techniques for green

NP synthesis. In this process, ammonium molybdate and elemental sulphur are mixed in 1:1 molar ratio in 10 ml of hydrazine monohydrate and 30 ml deionized water under magnetic stirring for 5 minutes. The resultant solvent mixture is transferred to a Teflon vessel and subjected to microwave radiation of 270 Watt in a microwave oven for 10 minutes, and is allowed to cool down naturally to room temperature. Black precipitate settled at the bottom of the solution is filtered, washed with distilled water, diluted hydrochloric acid and ethanol successively and centrifuged to remove any unreacted precursors. The final product is dried in vacuum oven at 50 degrees Celsius for 4 hours to obtain MoS<sub>2</sub> nanostructures. This technique qualifies for the energy efficient 'greener' approach by drastically reducing the reaction time (~300 times faster than the conventional method). Microwave radiation penetrates through Teflon vessel and interacts

**Table 1. Synthesis of silver nanoparticles using extracts from different parts of various plants**

Plants	Size (nm)	Plant's part	Shape	References
<i>Alternanthera dentate</i>	50–100	Leaves	Spherical	[27]
<i>Acorus calamus</i>	31.83	Rhizome	Spherical	[28]
<i>Boerhaavia diffusa</i>	25	whole plant	Spherical	[29]
Tea extract	20-90	Leaves	Spherical	[30]
<i>Tribulus terrestris</i>	16-28	Fruit	Spherical	[31]
<i>Abutilon indicum</i>	7-17	Leaves	Spherical	[32]
<i>Ziziphora tenuior</i>	8–40	Leaves	Spherical	[33]
<i>Cocous nucifera</i>	22	Inflorescence	Spherical	[34]
<i>Pistacia atlantica</i>	10–50	Seeds	Spherical	[35]

**Table 2. Nanoparticles of varying size and shape fabricated from fungal and yeast species**

Fungi and yeast	NPs	Size (nm)	Shapes	Location	Ref
<i>Alternaria alternate</i>	Au	12 ± 5	Spherical triangular hexagonal	Extracellular	[43]
<i>Aspergillus clavatus</i>	Au	24.4 ± 11	Triangular spherical hexagonal	Extracellular	[44]
<i>A. fumigatus</i>	ZnO	1.2–6.8	Spherical hexagonal	Extracellular	[45]
<i>A. oryzae</i> TFR9	FeCl <sub>3</sub>	10–24.6	Spherical	–	[46]
<i>A. sydowii</i>	Au	8.7–15.6	Spherical	Extracellular	[47]
<i>A. terreus</i>	Ag	1–20	Spherical	Extracellular	[48]
<i>A. tubingensis</i>	Ca <sub>3</sub> P <sub>2</sub> O <sub>8</sub>	28.2	Spherical	Extracellular	[49]
<i>Aureobasidium pullulans</i>	Au	29 ± 6	Spherical	Intracellular	[50]
<i>Candida albicans</i>	Au	5	Mono dispersed spherical	Cell-free extract	[51]
<i>C. glabrata</i>	CdS	–	–	Intracellular	[52]
<i>Coriolus versicolor</i>	Au	20–100, 100–300	Spherical ellipsoidal	Intra- and extracellular	[53]
<i>Cylindrocladium floridanum</i>	Au	19.05	Spherical	Extracellular	[54]
<i>Fusarium oxysporum</i>	Pt	70–180	Rectangular triangular spherical aggregates	Extracellular	[55]



Fig. 1. The various steps involved in the extraction of nanoparticles using plants [26]

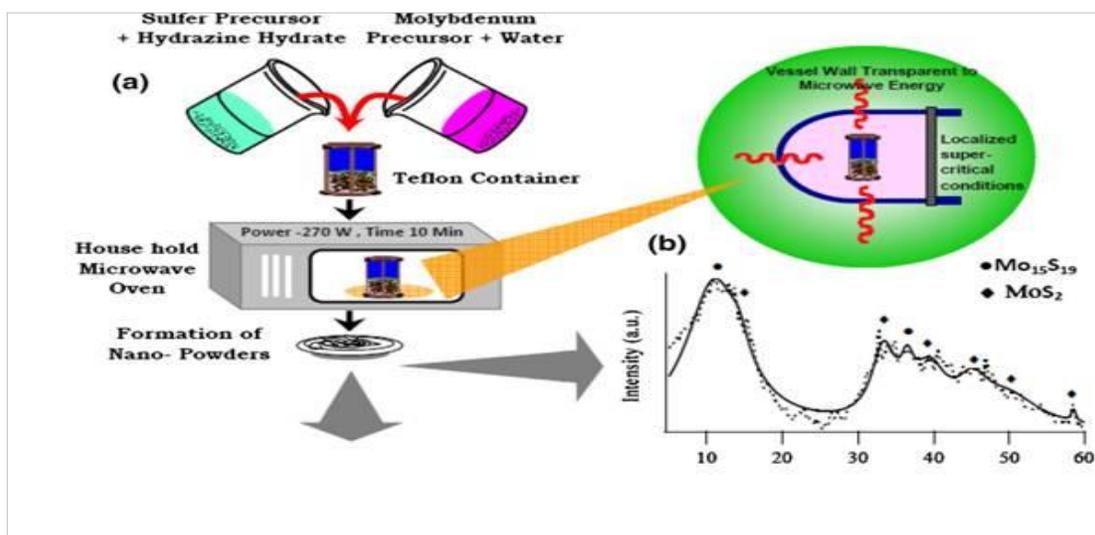


Fig. 2. The Schematics for microwave assisted green synthesis of Molybdenum disulphide nanoparticles [57]

with the solvents directly causing localized heating and thus generates supercritical conditions favorable for nucleation and growth of nanoparticles. The schematic illustration of the strategy for MW green synthesis of MSNs via generation of supercritical conditions is shown in Fig. 2 taken from the work of Qureshi et al. [57].

In their work they demonstrated interestingly, biofilm inhibition and antimicrobial behavior of MSNs produced using this method. This is a significant discovery since the biofilm protects pathogenic organisms from drugs and immune system by resisting entry and recognition, respectively. They also showed the MSNs to be

non-cytotoxic which gives them biocompatibility and increases their antimicrobial potential.

The green synthesis of Ag NPs with demonstrated antibacterial activity by Fatimah [21] using MW is another example of energy efficient green process for NP synthesis. The use of MW shows the rapid formation of Ag NPs with similar properties to those obtained through the time consuming aging method. In addition, the use of microwave irradiation yielded larger particles. The profound effect of irradiance on the reduction rate of AgNO<sub>3</sub> to Ag NPs using fig leaves extracts shown by Ulug et al. [58] is another instance of energy efficient green synthesis.

#### 4. DISEASE INHIBITION USING GREEN NPS

The excellent antibacterial, anti-parasitic and antitumor properties of green NPs allows them to play significant roles in medicine, clinical and *in vitro* diagnostic applications [8-12,18-25,51,57]; and also in agriculture, water treatment, food packaging and textiles [6,7,59-65]. Antibiotic resistance poses a major problem in healthcare due to the inherent tendency of microbial cells to alter their genes. In this context, the exploitation of inorganic NPs to develop antiseptics that are deadly to microbes and which demonstrate wide-range activity with lower prospects of microbial resistance is the most needed solution.

The use of Ag NPs in the biomedical sector has seen increasing number of applications with large number products such as ointments, dressing materials and body hygiene already in the market. Ag NPs have been reported to possess antimicrobial property against myriad array of pathogenic microorganisms. An excellent example is the work of Husseiny et al. [9] who showed the inhibitory capabilities of green Ag NPs towards bacteria and tumor. The NPs biosynthesized with '*Fusarium oxysporum*' showed excellent antibacterial activities when studied using agar well diffusion and zone of inhibition method against pathogenic strains of *E. coli* and *S. aureus*. Also, their work reveals

promising antitumor capability against human breast carcinoma cell line (MCF-7). Fig. 3 shows the antibacterial and antitumor activities taken from their work.

A serious concern is bacterial resistance to conventional antibiotics based on organic molecules. The prevalence of multidrug-resistant bacteria requires an effective solution and green NPs have come to the rescue. An example is the interesting microbial resistance mechanism using non-cytotoxic MSNs by reactive oxygen species (ROS) via disruption of cellular functions, as demonstrated in the work of Qureshi et al. [57]. Fig. 4 taken from their work compares and illustrates the effectiveness of MSNs with the reports of works for other inorganic NPs like Ag, Pd, Fe-Pt, Fe<sub>2</sub>O<sub>3</sub>, TiO<sub>2</sub>, ZnO, MgO, CuO [66-77] against various forms of bacteria.

In comparison to the noble metal Ag, which is one of the most investigated and well known NP for its antimicrobial properties, the cytotoxicity of MSNs is negligible and makes it more biocompatible and a comprehensive choice for all sorts of applications; Ag is limited in application by its higher cytotoxicity. Also, in comparison with the other NPs shown in Fig. 4 the MSNs have the lowest MIC (minimum inhibitory concentration) and MBC (minimum bactericidal concentration) values making it a more superior multidrug antibacterial solution.

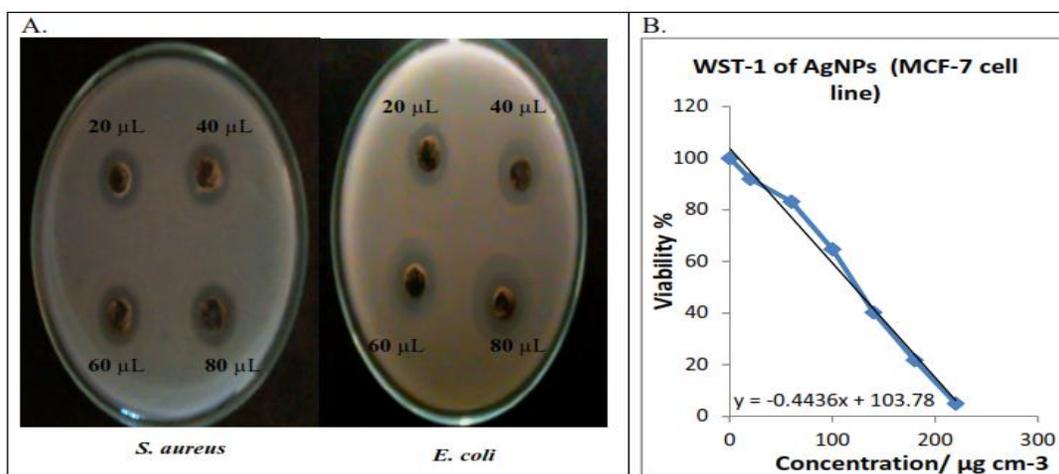
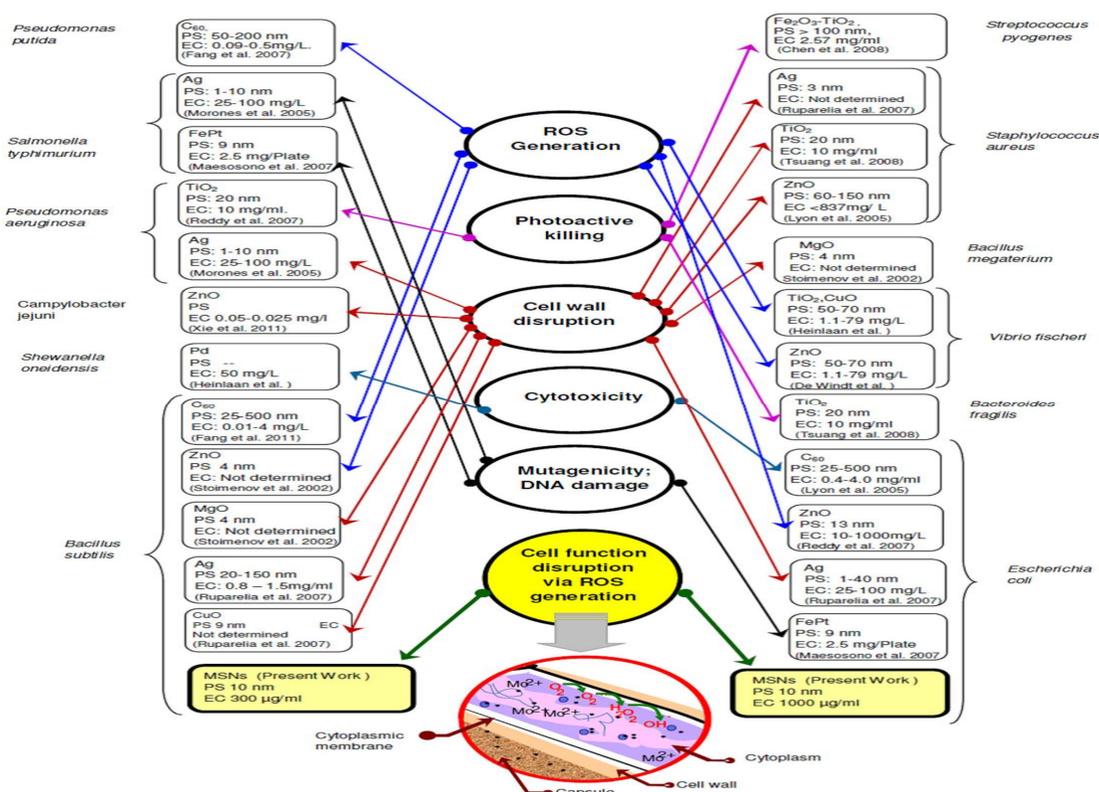


Fig. 3. The Antibacterial activity of different concentrations of biosynthesized AgNPs (A) against *E. coli* and *S. aureus* strains (B) viability chart of biosynthesized AgNPs against MCF-7 cell line. [9]



**Fig. 4. Comparative illustration showing the antimicrobial effect of different NPs with MSNs on various Gram-positive and Gram-negative bacteria [57]**

## 5.CONCLUSIONS

The use of natural and biogenic resources for the production of NPs is an eco-friendly, sustainable, inexpensive and contaminant free process that satisfies the requirements of energy saving, green and healthy environment protocols. The NPs synthesized in this manner from plants and microorganisms are less toxic, more stable, controlled, and beneficial to humans and environment as compared with those produced by physical/chemical methods. Moreover, such green NPs are very effective in treatment against pathogens and multi drug resistant bacteria due to their excellent antibiotic activities.

Microbes develop resistant strains in a short span of time to conventional organic based antibiotics which is a major health concern that needs an urgent and innovative solution. The wide range of antibiotic activities available from green inorganic NPs makes them ideal to develop antiseptics that are deadly to microbes and which have a low probability of promoting microbial resistance. The diversity of biogenic

resources and the multitude of NPs that can be synthesized with varying antimicrobial properties show the vast and rich possibilities in the field of green synthesis. An increased awareness to the health benefits of the green route of synthesizing NPs is desired along with renewed research to bring to light new and exciting discoveries in this direction.

## COMPETING INTERESTS

Authors have declared that no competing interests exist.

## REFERENCES

1. Basu S, Bhattacharyya P. Recent developments on graphene and graphene oxide based solid state gas sensors. Sens. Actuators B. 2012;173:1-21.
2. Yue Q, Shao Z, Chang S, Li J. Adsorption of gas molecules on monolayer MoS<sub>2</sub> and effect of applied electric field. Nanoscale Res. Lett. 2013;8:425.

3. Ramanathan AA. Defect functionalization of MoS<sub>2</sub> nanostructures as toxic gas sensors. IOP Conf. Ser. Mater. Sci. Eng. 2018;305:012001.
4. Luo H, Cao Y, Zhou J, Feng J, Cao J, Guo H. Adsorption of NO<sub>2</sub>, NH<sub>3</sub> on monolayer MoS<sub>2</sub> doped with Al, Si, and P: A first-principles study. Chemical Physics Letters. 2016;643:27–33.
5. Najmaei S, Yuan J, Zhang J, Ajayan P, Lou J. Synthesis and defect investigation of two-dimensional molybdenum disulfide atomic layers. Acc. Chem. Res. 2015; 48(1):31–40.
6. Khot LR, Sankaran S, Maja JM, Ehsani R, Schuster EW. Applications of nanomaterials in agricultural production and crop protection: A review. Crop Prot. 2012;35:64–70.
7. Kottegoda N, et al. Urea hydroxyapatite nanohybrids for slow release of nitrogen. ACS Nano. 2017;11:1214–1221.
8. Chauhan A, Zubair S, Tufail S, Sherwani A, Sajid M, Raman SC, Azam A, Owais M. Fungus-mediated biological synthesis of gold nanoparticles: Potential in detection of liver cancer. Int J Nanomedicine. 2011;6: 2305–2319.
9. Husseiny SM, Salah TA, Anter HA, Biosynthesis of size controlled silver nanoparticles by *Fusarium oxysporum*, their antibacterial and antitumor activities, Beni-Suef University. Journal of Basic and Applied sciences. 2015;4:225–231.
10. Ahmed S, Ahmad M, Swami BL, Ikram S. A review on plants extract mediated synthesis of silver nanoparticles for antimicrobial applications: A green expertise. Journal of Advanced Research. 2016;7:17–28.
11. Santhoshkumar J, Venkat Kumar S, Rajeshkumar S. Synthesis of zinc oxide nanoparticles using plant leaf extract against urinary tract infection pathogen. Resource-Efficient Technologies. 2017;3: 459–465.
12. Loureiro A, Azoia NG, Gomes AC, Cavaco-Paulo A. Albumin-based nanodevices as drug carriers. Curr. Pharm. Des. 2016;22:1371–1390.
13. Ramanathan AA, Aqra MW, Al-Rawajfeh AE. Recent advances in 2D-nanopores for desalination. Environmental Chemistry Letters; 2018. DOI:10.1007/s10311-018-0745-4
14. Ramanathan AA, Khalifeh JM. Enhanced thermoelectric properties of suspended mono and bilayer of MoS<sub>2</sub> from first principles. TNANO; 2018. DOI:10.1109/TNANO.2018.2841640
15. Avasare V, et al. Room-temperature synthesis of TiO<sub>2</sub> nanospheres and their solar driven photoelectrochemical hydrogen production. Int. J. Energy Res. 2015;39:1714-1719.
16. Beeler E, Singh OV. Extremophiles as sources of inorganic bio-nanoparticles. World J. Microbiol. Biotechnol. 2016;32: 156. DOI:10.1007/s11274-016-2111-7
17. Singh R, Shedbalkar UU, Wadhvani SA, Chopade BA. Bacteriogenic silver nanoparticles: Synthesis, mechanism, and applications. Appl. Microbiol. Biotechnol. 2015;99:4579–4593. DOI: 10.1007/s00253-015-6622-1
18. Alghuthaymi MA, Almoammar H, Rai M, Said-Galiev E, Abd-Elsalam KA. Myconanoparticles: Synthesis and their role in phytopathogens management. Biotechnol. Biotechnol. Equip. 2015;29: 221–236. DOI:10.1080/13102818.2015.1008194
19. Boroumand Moghaddam A, Namvar F, Moniri M, Md Tahir P, Azizi S, Mohamad R. Nano particles biosynthesized by fungi and yeast: A review of their preparation, properties, and medical applications. Molecules. 2015;20:16540–16565. DOI:10.3390/molecules200916540
20. Kumar D, Karthik L, Kumar G, Roa KB. Biosynthesis of silver nanoparticles from marine yeast and their antimicrobial activity against multidrug resistant pathogens. Pharmacologyonline. 2011;3:1100–1111.
21. Fatimah IS. Green synthesis of silver nanoparticles using extract of *Parkia speciosa* Hassk pods assisted by microwave irradiation. Journal of Advanced Research. 2016;961-969.
22. Lori Rastogi, Arunachalam J. Sunlight based irradiation strategy for rapid green synthesis of highly stable silver nanoparticles using aqueous garlic (*Allium sativum*) extract and their antibacterial potential. Materials Chemistry and Physics. 2011;129:558-563.
23. Kuber C, Bhainsa SF D'Souza. Extracellular biosynthesis of silver nanoparticles using the fungus *Aspergillus fumigatus*. Biointerfaces. 2006;47:160-164.
24. Balakumaran MD, Ramachandran R, Balashanmugam P, Mukeshkumar DJ, Kalaichelvan PT. Mycosynthesis of silver

- and gold nanoparticles: Characterization optimization, and antimicrobial activity against human pathogens. *Microbiological Research*. 2016;182:8–20.
25. Azmath P, Baker S, Rakshith D, Satish S. Mycosynthesis of silver nanoparticles bearing antibacterial activity. *Saudi Pharmaceutical Journal*. 2016;24:140–146.
  26. Amarendra DD, Gopal K. Biosynthesis of silver and gold nanoparticles using *Chenopodium album* leaf extract. *Colloid Surface A*. 2010;27:33.
  27. Kumar DA, Palanichamy V, Roopan SM. Green synthesis of silver nanoparticles using *Alternanthera dentata* leaf extract at room temperature and their antimicrobial activity. *Spectrochim Acta Part A: Mol Biomol Spectrosc*. 2014;127:168–71.
  28. Nakkala JR, Mata R, Kumar Gupta A, Rani Sadras S. Biological activities of green silver nanoparticles synthesized with *Acorus calamus* rhizome extract. *Eur J Med Chem*. 2014;85:784–94.
  29. Nakkala JR, Mata R, Gupta AK, Sadras SR. Green synthesis and characterization of silver nanoparticles using *Boerhavia diffusa* extract and their antibacterial activity. *Indus Crop Prod*. 2014;52:562–6.
  30. Suna Q, Cai X, Li J, Zheng M, Chenb Z, Yu CP. Green synthesis of silver nanoparticles using tea leaf extract and evaluation of their stability and antibacterial activity. *Colloid Surf A: Physicochem Eng Aspects*. 2014;444:226–31.
  31. Gopinatha V, Ali MD, Priyadarshini S, Meera Priyadarshini N, Thajuddinb N, Velusamy P. Biosynthesis of silver nanoparticles from *Tribulus terrestris* and its antimicrobial activity: A novel biological approach. *Colloid Surf B: Biointerface*. 2012;96:69–74.
  32. Ashok kumar S, Ravi S, Kathiravan V, Velmurugan S. Synthesis of silver nanoparticles using *Abutilon indicum* leaf extract and their antibacterial activity. *Spectrochim Acta Part A: Mol Biomol Spectrosc*. 2015;134:34–9.
  33. Sadeghi B, Gholamhoseinpoor F. A study on the stability and green synthesis of silver nanoparticles using *Ziziphora tenuior* (Zt) extract at room temperature. *Spectrochim Acta Part A: Mol Biomol Spectrosc*. 2015;134:310–5.
  34. Mariselvam R, Ranjitsingh AJA, Usha Raja Nanthini A, Kalirajan K, Padmalatha C, Selvakumar MP. Green synthesis of silver nanoparticles from the extract of the inflorescence of *Cocos nucifera* (Family: Arecaceae) for enhanced antibacterial activity. *Spectrochim Part A: Mol Biomol Spectrosc*. 2014;129:537–41.
  35. Sadeghi B, Rostami A, Momeni SS. Facile green synthesis of silver nanoparticles using seed aqueous extract of *Pistacia atlantica* and its antibacterial activity. *Spectrochim Part A: Mol Biomol Spectrosc*. 2015;134:326–32.
  36. Dahoumane SA, Wujcik EK, Jeffryes C. Noble metal, oxide and chalcogenide-based nanomaterials from scalable phototrophic culture systems. *Enzyme Microb. Technol*. 2016;95:13–27. DOI:10.1016/j.enzmictec.2016.06.008 [PubMed]
  37. Borovaya MN, Naumenko AP, Matvieieva NA, Blume YB, Yemets AI. Biosynthesis of luminescent CdS quantum dots using plant hairy root culture. *Nanoscale Res. Lett*. 2014;9:686. DOI:10.1186/1556-276X-9-686
  38. Mahdavi M, Namvar F, Ahmad MB, Mohamad R. Green biosynthesis and characterization of magnetic iron oxide (Fe<sub>3</sub>O<sub>4</sub>) nanoparticles using seaweed (*Sargassum muticum*) aqueous extract. *Molecules*. 2013;18:5954–5964. DOI:10.3390/molecules18055954
  39. Noruzi M. Biosynthesis of gold nanoparticles using plant extracts. *Bioprocess. Biosyst. Eng*. 2015;38:1–14. DOI:10.1007/s00449-014-1251-0
  40. Blackwell M. The fungi: 1, 2, 3... 5.1 million species? *Am. J. Bot*. 2011;98:426–438.
  41. Castro-Longoria E, Vilchis-Nestor AR, Avalos-Borja M. Biosynthesis of silver, gold and bimetallic nanoparticles using the filamentous fungus *Neurospora crassa*. *Colloids Surf. B Biointerfaces*. 2011;83:42–48.
  42. Kitching M, Ramani M, Marsili E. Fungal biosynthesis of gold nanoparticles: Mechanism and scale up. *Microb. Biotechnol*. 2015;8:904–917. DOI: 10.1111/1751-7915.12151 [PMC free article] [PubMed]
  43. Sarkar J, Ray S, Chattopadhyay D, Laskar A, Acharya K. Mycogenesis of gold nanoparticles using a phytopathogen *Alternaria alternata*. *Bioprocess Biosyst Eng*. 2012;35:637–643.
  44. Verma VC, Singh SK, Solanki R, Prakash S. Biofabrication of anisotropic gold nanotriangles using extract of endophytic *Aspergillus clavatus* as a dual functional

- reductant and stabilizer. *Nanoscale Res Lett.* 2011;6:16–22.  
DOI:10.1186/1556-276X-6-261
45. Raliya R, Tarafdar JC. ZnO nanoparticle biosynthesis and its effect on phosphorous-mobilizing enzyme secretion and gum contents in cluster bean (*Cyamopsis tetragonoloba* L.). *Agirc Res.* 2013;2:48–57.
  46. Raliya R. Rapid, low-cost, and ecofriendly approach her for iron nanoparticle synthesis using *Aspergillus oryzae* TFR9. *J Nanopart.* 2013;141274:4.
  47. Vala AK. Exploration on green synthesis of gold nanoparticles by a marine-derived fungus *Aspergillus sydowii*. *Environ Prog Sustain Energy.* 2015;34:194–197.
  48. Li G, He D, Qian Y, Guan B, Gao S, Cui Y, Yokoyama K, Wang L. Fungus-mediated green synthesis of silver nanoparticles using *Aspergillus terreus*. *Int J Mol Sci.* 2012;13:466–476.
  49. Tarafdar JC, Raliya R, Rathore I. Microbial synthesis of phosphorous nanoparticle from tri-calcium phosphate using *Aspergillus tubingensis* TFR-5. *J Bionanosci.* 2012;6:84–89.
  50. Zhang X, He X, Wang K, Yang X. Different active biomolecules involved in biosynthesis of gold nanoparticles by three fungus species. *J Biomed Nanotechnol.* 2011;7:245–254.
  51. Ahmad T, Wani IA, Manzoor N, Ahmed J, Asiri AM. Biosynthesis, structural characterization and antimicrobial activity of gold and silver nanoparticles. *Colloids Surf B: Biointerfaces.* 2013;107:227–234.
  52. Krumov N, Oder S, Perner Nochtla I, Angelov A, Posten C. Accumulation of CdS nanoparticles by yeasts in a fed-batch bioprocess. *J Biotechnol.* 2007;132:481–486.
  53. Sanghi R, Verma P. pH dependant fungal proteins in the “green” synthesis of gold nanoparticles. *Adv Mater Lett.* 2010;1:193–199.
  54. Narayanan KB, Sakthivel N. Mycocrystallization of gold ions by the fungus *Cylindrocladium floridanum*. *World J Microbiol Biotechnol.* 2013;29:2207–2211.
  55. Govender Y, Riddin T, Gericke M, Whiteley CG. Bioreduction of platinum salts into nanoparticles: A mechanistic perspective. *Biotechnol Lett.* 2009;31:95–100.
  56. Shinde MD, Chavan PG, Umarji GG, Arbuj SS, Rane SB, More MA, Joag DS, Amalnerkar DP. Field emission and photocatalytic investigations on hierarchical nanostructures of copper doped CdS synthesized by ‘kitchen-chemistry’ approach. *J Nanosci Nanotechnol.* 2012;12:3788–3798.
  57. Qureshi N, Patil R, Shinde M, Umarji G, Causin V, Gade W, Mulik U, Bhalerao A, Dinesh P, Amalnerkar DP. Innovative biofilm inhibition and anti-microbial behavior of molybdenum sulfide nanostructures generated by microwave-assisted solvothermal route. *Appl Nanosci.* 2015;5:331–341.
  58. Ulug B, HalukTurkdemir M, Cicek A, Mete A. Role of irradiation in the green synthesis of silver nanoparticles mediated by fig (*Ficus carica*) leaf extract. *Spectrochim Part A: Mol Biomol Spectrosc.* 2015;135: 153–61.
  59. Raliya R. Rapid, low-cost, and ecofriendly approach her for iron nanoparticle synthesis using *Aspergillus oryzae* TFR9. *J. Nanoparticles;* 2013.  
DOI:10.1155/2013/141274
  60. Tarafdar JC, Raliya R, Rathore I. Microbial synthesis of phosphorous nanoparticle from tri-calcium phosphate using *Aspergillus tubingensis* TFR-5. *J. Bionanosci.* 2012;6:84–89.
  61. Dimapilis ES, Hsu CS, Mendoza RO, Lu MC. Zinc oxide nanoparticles for water disinfection. *Sustainable Environment Research.* 2018;28:47-56.
  62. Lu H, Wang J, Stoller M, Wang T, Bao Y, Hao H. An overview of nanomaterials for water and wastewater treatment. *Advances in Materials Science and Engineering;* 2016.  
DOI:10.1155/2016/4964828
  63. Espitia PJP, Soares NFF, Coimbra JSR, de Andrade NJ, Cruz RS, Medeiros EAA. Zinc Oxide Nanoparticles: Synthesis, antimicrobial activity and food packaging applications. *Food Bioprocess Technol.* 2012;5:1447-1464.
  64. Abramova A, Gedanken A, Popov V, Ooi E-H, Mason TJ, Joyce EM, Beddow J, Perelshtein I, Bayazitov V. A sonochemical technology for coating of textiles with antibacterial nanoparticles and equipment for its implementation. *Materials Letters.* 2013;96:121-124.
  65. Zahid M, Papadopoulou EL, Suarato G, Binas VD, Kiriakidis G, Gounaki I, Moira O, Venieri D, Ilker S, Bayer IS, Athanassiou A. Fabrication of visible light-induced

- antibacterial and self-cleaning cotton fabrics using manganese doped TiO<sub>2</sub> nanoparticles. ACS Applied Bio Materials. 2018;1(4):1154-1164.  
DOI: org/ 10.1021/acsabm.8b00357
66. Fang J, Lyon DY, Wiesner MR, Dong J, Alvarez PJ, Effect of a fullerene water suspension on bacterial phospholipids and membrane phase behavior. Environ Sci Technol. 2007;41:2636–2642.
  67. Chen WJ, Tsai PJ, Chen YC, Functional Fe<sub>3</sub>O<sub>4</sub>/TiO<sub>2</sub> core/shell magnetic nanoparticles as photokilling agents for pathogenic bacteria. Small. 2008;4:485–489.
  68. Maenosono S, Suzuki T, Saita S, Mutagenicity of water-soluble FePt nanoparticles in Ames test. J Toxicol Sci. 2007;32:575–579.
  69. Morones JR, Elechiguerra JL, Camacho A, Holt K, Kouri JB, Ramírez JT, Yacaman MJ, The bactericidal effect of silver nanoparticles. Nanotechnology. 2005;16: 2346–2353.
  70. Ruparelia JP, Chatterjee AK, Duttagupta SP, Mukherji S. Strain specificity in antimicrobial activity of silver and copper nanoparticles. Acta Biomater. 2007;4:707–716.
  71. Reddy KM, Feris K, Bell J, Wingett DG, Hanley C, Punnoose A, Selective toxicity of zinc oxide nanoparticles to prokaryotic and eukaryotic systems. Appl Phys Lett. 2007;90:2139021–2139023.
  72. Tsuang YH, Sun JS, Huang YC, Lu CH, Chang WH, Wang CC. Studies of photo killing of bacteria using titanium dioxide nanoparticles. Artif Organs. 2008;32:167–174.
  73. Lyon DY, Fortner JD, Sayes CM, Colvin VL, Hughe JB, Bacterial cell association and antimicrobial activity of a C60 water suspension. Environ Toxicol Chem. 2005;24:2757–2762.
  74. Heinlaan M, Ivask A, Blinova I, Dubourguier HC, Kahru A. Toxicity of nanosized and bulk ZnO, CuO and TiO<sub>2</sub> to bacteria *Aliivibrio fischeri* and crustaceans *Daphnia magna* and *thamnocephalus platyurus*. Chemosphere. 2008;71:1308–1316.
  75. Stoimenov PK, Klinger RL, Marchin GL, Klabunde KJ. Metal oxide nanoparticles as bactericidal agents. Langmuir. 2002;18: 6679-6686.
  76. Xie Y, He Y, Irwin PL, Jin T, Shi X. Antibacterial activity and mechanism of action of zinc oxide nanoparticles against *Campylobacter jejuni*. Appl Environ Microbiol. 2011;77:2325–2331.
  77. De Windt W, Boon N, Van den Bulcke J, Rubberecht L, Prata F, Mast J, Hennebel T, Verstraete W. Biological control of the size and reactivity of catalytic Pd(0) produced by *Shewanella oneidensis*. Antonie Van Leeuwenhoek. 2006;90:377–389.

© 2019 Ramanathan and Aqra; This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:

The peer review history for this paper can be accessed here:  
<http://www.sdiarticle3.com/review-history/46014>